

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

# Oxygen-participated Electrochemistry of New Lithium-rich Layered Oxides $\text{Li}_3\text{MRuO}_5$ (M = Mn, Fe)

S. Laha,<sup>a</sup> S. Natarajan,<sup>a</sup> J. Gopalakrishnan,<sup>\*a</sup> E. Morán,<sup>b</sup> R. Sáez-Puche,<sup>b</sup> M. Á. Alario-Franco,<sup>b,c</sup> A. J. Dos Santos-García,<sup>b</sup> J.C. Pérez-Flores,<sup>c</sup> A. Kuhn,<sup>c</sup> F. García-Alvarado,<sup>\*c</sup>

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x

We describe the synthesis, crystal structure and lithium deinsertion/insertion electrochemistry of two new lithium-rich layered oxides,  $\text{Li}_3\text{MRuO}_5$  (M = Mn, Fe), related to  $\text{Li}_2\text{MnO}_3$  and  $\text{LiCoO}_2$ . The M = Mn oxide adopts a structure related to  $\text{Li}_2\text{MnO}_3$  ( $C2/m$ ) where Li and  $(\text{Li}_{0.2}\text{Mn}_{0.4}\text{Ru}_{0.4})$  layers alternate along the  $c$ -axis, while the M = Fe oxide adopts a near-perfect  $\text{LiCoO}_2$  ( $R-3m$ ) structure where Li and  $(\text{Li}_{0.2}\text{Fe}_{0.4}\text{Ru}_{0.4})$  layers are stacked alternately. Magnetic measurements indicate for  $\text{Li}_3\text{MnRuO}_5$  the presence of  $\text{Mn}^{3+}$  and low spin configuration for  $\text{Ru}^{4+}$  where the itinerant electrons are occupying a  $\pi^*$  band. The onset of a net maximum in the  $\chi$  vs. T plot at 9.5 K and the negative value of the Weiss constant ( $\theta$ ) of -31.4 K indicate the presence of antiferromagnetic superexchange interactions according to different pathways. Lithium electrochemistry shows a similar behaviour for both oxides and related to the typical behaviour of Li-rich layered oxides where participation of oxide ion in the electrochemical processes is usually found. A long first charge process with capacities of  $240 \text{ mAhg}^{-1}$  (2.3 Li/f.u.) and  $144 \text{ mAhg}^{-1}$  (1.38 Li/f.u.) is observed for M = Mn and M = Fe, respectively. An initial sloping region (OCV to ca. 4.1 V) is followed by a long plateau (ca. 4.3 V). Further discharge – charge cycling points to partial reversibility (ca.  $160 \text{ mAhg}^{-1}$  and  $45 \text{ mAhg}^{-1}$  for Mn and Fe, respectively). Nevertheless, just after a few cycles, cell failure is observed. X-ray photoelectron spectroscopy (XPS) characterisation of both pristine and electrochemically oxidized  $\text{Li}_3\text{MRuO}_5$  reveals that in the M = Mn oxide,  $\text{Mn}^{3+}$  and  $\text{Ru}^{4+}$  are partially oxidized to  $\text{Mn}^{4+}$  and  $\text{Ru}^{5+}$  in the sloping region at low voltage, while in the long plateau,  $\text{O}^{2-}$  is also oxidized. Oxygen release likely occurs which may be the origin of cells' failure on cycling. Interestingly, some other Li-rich layered oxides have been reported to cycle acceptably even with the participation of  $\text{O}^{2-}$  ligand in the reversible redox processes. In the M = Fe oxide, the oxidation process appears to affect only to Ru (4+ to 5+ in the sloping region) and  $\text{O}^{2-}$  (plateau) while Fe seems to retain its 3+ state.

## Introduction

There is a great interest to develop new cathode materials for Li-ion batteries based on layered oxides related to  $\text{LiCoO}_2$  and  $\text{Li}_2\text{MnO}_3$ .<sup>1, 2</sup> We have recently explored two series of rock salt related oxides,<sup>3, 4</sup>  $\text{Li}_3\text{M}_2\text{RuO}_6$  and  $\text{Li}_3\text{MRuO}_5$  (M = Co, Ni), towards lithium deinsertion/insertion electrochemistry, of which the latter showed attractive specific capacities (ca.  $200 \text{ mAhg}^{-1}$ ). The promising discharge capacities of the  $\text{Li}_3\text{MRuO}_5$  (M = Co, Ni) presumably arise from (1) the lithium-rich layered rock salt structure similar to  $\text{Li}(\text{Li}_{0.17}\text{Ni}_{0.25}\text{Mn}_{0.58})\text{O}_2$ <sup>5</sup>, (2) the redox characteristics of Co/Ru and Ni/Ru in these materials.<sup>3</sup> and (3) the participation of the oxide ions,  $\text{O}^{2-}$ , in the electrochemical

processes. In view of the foregoing, we considered relevant to investigate other  $\text{Li}_3\text{MRuO}_5$  compositions for M = Mn, Fe and Cu. Herein we report the synthesis, structural and magnetic characterization and lithium deinsertion-insertion electrochemistry of these materials. We also report XPS characterisation of pristine and lithium-deinserted  $\text{Li}_3\text{MRuO}_5$  (M = Mn, Fe). Finally, we compare the present results and those earlier reported on  $\text{Li}_3\text{MRuO}_5$  (M = Co, Ni)<sup>3</sup> and other Li-rich layered materials to draw a general conclusion. In the case of  $\text{Li}_3\text{MRuO}_5$  the participation of oxide ions in the redox process seems to influence the electrochemical properties as expected by the presence of Li in the transition metal (TM) layer. However, for this particular compound lower reversibility, probably due to

enhanced oxygen loss, drive to cell failure on cycling in spite of the attractive high capacity developed in the first cycles.

## Experimental

### Synthesis

We attempted to prepare  $\text{Li}_3\text{MRuO}_5$  for  $M = \text{Mn, Fe and Cu}$  by the ceramic route involving solid state reaction of stoichiometric mixtures of  $\text{Li}_2\text{CO}_3$ ,  $\text{MC}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$  ( $M = \text{Mn, Fe}$ )/ $\text{CuO}$  and  $\text{RuO}_2$  (pre-dried overnight at  $125^\circ\text{C}$ ). While we succeeded in preparing a single-phase  $\text{LiCoO}_2$ -like  $\text{Li}_3\text{FeRuO}_5$  by this method, we could

not prepare the analogous Mn compound. However the Mn analogue was successfully prepared by the following method: first,  $\text{Li}_3\text{RuO}_4$  precursor was prepared by reacting stoichiometric quantities of  $\text{Li}_2\text{CO}_3$  and  $\text{RuO}_2$ .<sup>6</sup> In the second step,  $\text{Li}_3\text{RuO}_4$  was stoichiometrically mixed with  $\text{MnC}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$  and the mixture was reacted at  $1250^\circ\text{C}$  to obtain  $\text{Li}_3\text{MnRuO}_5$  as single phase. The exact synthesis conditions are summarized in Table 1. Finally, a Cu analogue but with a more complex structure (see later) was synthesized.

**Table 1.** Conditions for the synthesis of  $\text{Li}_3\text{MRuO}_5$  ( $M = \text{Mn, Fe, Cu}$ ).

Composition	Starting materials	Synthesis conditions ( $^\circ\text{C, h}$ ) <sup>a</sup>	Result
$\text{Li}_3\text{MnRuO}_5$	$\text{Li}_2\text{CO}_3 + \text{MnC}_2\text{O}_4 \cdot 2\text{H}_2\text{O} + \text{RuO}_2$	900, 12; 925, 12	$\text{Li}_2\text{MnO}_3 + \text{RuO}_2$
$\text{Li}_3\text{MnRuO}_5$	$\text{Li}_3\text{RuO}_4 + \text{MnC}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$	900, 12; 1250, 24 (pellet), (*R)	$\text{Li}_3\text{MnRuO}_5$
$\text{Li}_3\text{FeRuO}_5$	$\text{Li}_2\text{CO}_3 + \text{FeC}_2\text{O}_4 \cdot 2\text{H}_2\text{O} + \text{RuO}_2$	900, 12; 925, 12 (*R)	$\text{Li}_3\text{FeRuO}_5$
$\text{Li}_3\text{CuRuO}_5$	$\text{Li}_2\text{CO}_3 + \text{CuO} + \text{RuO}_2$	900, 12; 925, 12 (*R)	$\text{Li}_3\text{CuRuO}_5$

<sup>a</sup> \*R indicates repeated heating with intermittent grinding at these conditions until the formation of the single phase Footnote text.

### Structural characterisation

Formation of single phase products and their crystal structures were studied by means of powder X-ray diffraction (PXRD). PXRD patterns were recorded with a PANalytical X'Pert diffractometer operated at 40 kV and 30 mA using Ni-filtered  $\text{Cu K}\alpha$  radiation. For Rietveld refinement, the data were collected in the  $2\theta$  range  $5 - 90^\circ$  with a step size of  $0.02^\circ$  and step duration of 50 s. Rietveld refinements of the structures were carried out employing the program GSAS.<sup>7</sup> A sixth order Chebychev polynomial for the background, zero, LP factor, scale, pseudo-Voigt profile function (U, V, W and X), lattice parameters, atomic coordinates and  $B_{\text{iso}}$  (total 23 parameters) were used in the refinement. Thermal parameters were constrained to be the same for atoms occupying the same site. PXRD patterns were simulated using the program POWDERCELL.<sup>8</sup>

### Magnetic characterisation

Magnetic susceptibility measurements were performed in a Quantum Design XL Squid magnetometer in the temperature range 2-300 K at 5 mT. The magnetic susceptibility data were collected after cooling the sample from room temperature to 2 K in a zero field (ZFC) and after cooling in the measuring field (FC). Magnetization was measured at different temperatures in magnetic field strengths up to 5 T.

### Electrochemical studies

Electrochemical characterisation of  $\text{Li}_3\text{MRuO}_5$  ( $M = \text{Mn and Fe}$ ) was carried out by galvanostatic and potentiostatic methods on

two electrode cells using a VMP3 system (BioLogic). Positive electrodes were prepared by mixing the corresponding active material,  $\text{Li}_3\text{MRuO}_5$ , with Super S carbon black (Cabot Corp.) and a binder (Kynarfex, Elf Atochem) in 85:10:5 weight ratio, respectively. Pellets of 8 mm diameter, having  $\approx 17$  mg of active material, were obtained by uniaxial pressing and drying at  $80^\circ\text{C}$  for overnight. Coin-type cells (CR2032) were assembled in an argon-filled glove box. A lithium disk was used as the negative electrode, 1M  $\text{LiPF}_6$  in a 50:50 mixture of ethylene carbonate (EC): dimethyl carbonate (DMC) (LP30, Basf) as the electrolyte and a disk of glass-fiber paper (Whatman) as the separator.

Galvanostatic cycling properties were evaluated at constant current ( $\approx C/20$  rate, being 20 the necessary hours to insert 1 Li/formula unit -f.u., hereafter-) in the 3.0 - 4.5 V potential range and at room temperature. Stepped-potential chronoamperometry (CA) experiments were performed in the same potential range by applying 10 mV every hour.

Synthesis of electrochemically deinserted  $\text{Li}_{3-x}\text{MRuO}_5$  samples was accomplished by potentiostatic charge up to selected potentials (see below) of lithium cells. Cells were kept at the selected potentials until the current fell below  $5 \times 10^{-4}$  mA in order to achieve equilibrium conditions.

### X-ray photoelectron spectroscopy (XPS) characterisation

XPS measurements of the pristine materials and electrochemically oxidized samples,  $\text{Li}_3\text{MnRuO}_5$  (4.15 and 4.50 V) and  $\text{Li}_3\text{FeRuO}_5$  (3.80 and 4.50 V) were carried out with Kratos Axis Ultra DLD Spectrometer, using a focused monochromatised Al- $\text{K}\alpha$  radiation (1486.708 eV). The pressure inside the chamber was kept around  $5 \times 10^{-9}$  mbar during the

measurements. The peak positions of all the spectra were corrected to the C1s core level peak at 284.6 eV. Core peaks were analyzed using non-linear Shirley-type background. The positions of the peaks and area under the curves were optimized by a weighted least-squares fitting method employing XPSpeak41 software.

## Results and Discussion

### Structural characterisation

The PXRD patterns of  $\text{Li}_3\text{MRuO}_5$  ( $M = \text{Mn, Fe and Cu}$ ) are presented in Fig. 1. The PXRD patterns of  $M = \text{Mn and Fe}$  indicate the formation of single phase rock salt related structures of  $\text{Li}_2\text{MnO}_3$  and  $\text{LiCoO}_2$  type, respectively.<sup>9, 10</sup> The PXRD pattern of  $\text{Li}_3\text{CuRuO}_5$  also shows a  $\text{LiCoO}_2/\text{Li}_2\text{MnO}_3$  rock salt related structure, but we could not index the pattern in either of the above mentioned model oxides.

Considering the similarity of PXRD pattern of  $\text{Li}_3\text{MnRuO}_5$  with  $\text{Li}_2\text{MnO}_3$ ,<sup>9</sup> we could refine the crystal structure of  $\text{Li}_3\text{MnRuO}_5$  on the basis of the monoclinic  $\text{Li}_2\text{MnO}_3$  ( $C2/m$ ) model. The refined atomic coordinates and isotropic temperature factors are presented in Table 2, the bond lengths in Table 3 while the final Rietveld profile fit is shown in Figure 2.

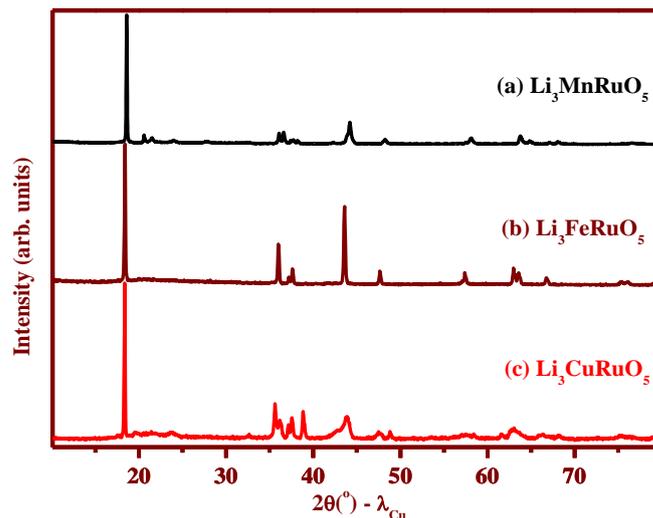


Fig. 1 PXRD patterns of  $\text{Li}_3\text{MRuO}_5$ : (a)  $M = \text{Mn}$ ; (b)  $M = \text{Fe}$ ; (c)  $M = \text{Cu}$

Table 2. Atomic coordinates and isotropic displacement parameters ( $U_{\text{iso}}$ ) for  $\text{Li}_3\text{MnRuO}_5$ . Space group  $C2/m$ ,  $a = 5.063(1) \text{ \AA}$ ,  $b = 8.639(1) \text{ \AA}$ ,  $c = 5.088(1) \text{ \AA}$ ,  $\beta = 109.41(1)^\circ$

Atom	site	x	y	z	$U_{\text{iso}}$	Occupancy
Li	2(b)	0	0.5	0	0.019(2)	0.585(4)
Mn	2(b)	0	0.5	0	0.019(2)	0.208(4)
Ru	2(b)	0	0.5	0	0.019(2)	0.208(4)
Li	2(c)	0	0	0.5	0.131(2)	1.0
Li	4(h)	0	0.319(1)	0.5	0.085(1)	0.959(2)
Mn	4(h)	0	0.319(1)	0.5	0.085(1)	0.021(2)
Ru	4(h)	0	0.319(1)	0.5	0.085(1)	0.021(2)
Li	4(g)	0	0.168(2)	0	0.038(1)	0.050(9)
Mn	4(g)	0	0.168(2)	0	0.038(1)	0.476(9)
Ru	4(g)	0	0.168(2)	0	0.038(1)	0.476(9)
O	4(i)	0.224(1)	0	0.225(1)	0.039(1)	1.0
O	8(j)	0.253(1)	0.325(1)	0.228(1)	0.028(1)	1.0

Reliability Factors:  $R_p = 6.97\%$ ,  $R_{wp} = 9.79\%$ ,  $R_f = 10.70\%$ ,  $\chi^2 = 2.13$


Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxxx

ARTICLE TYPE

**Table 3** Bond distances (Å) for  $\text{Li}_3\text{MnRuO}_5$ 

	Bond length / Å	BVS
Li/Mn/Ru(2b) – O(4i)	2.080(1)×2	Li: 1.16 ; Mn: 2.57; Ru: 3.14
– O(8j)	2.071(2)×4	
Li(2c) – O(4i)	2.074(4)×2	Li: 1.02
– O(8j)	2.151(3)×4	
Li/Mn/Ru(4h)– O(8j)	1.968(1)×2	Li: 1.16 ; Mn: 2.57 ; Ru: 3.14
– O(8j)	2.178(1)×2	
– O(4i)	2.248(1)×2	
Li/Mn/Ru(4g) – O(4i)	1.963(1)×2	Li: 1.57 ; Mn: 3.48 ; Ru: 4.25
– O(8j)	1.953(1)×2	
– O(8j)	1.968(1)×2	
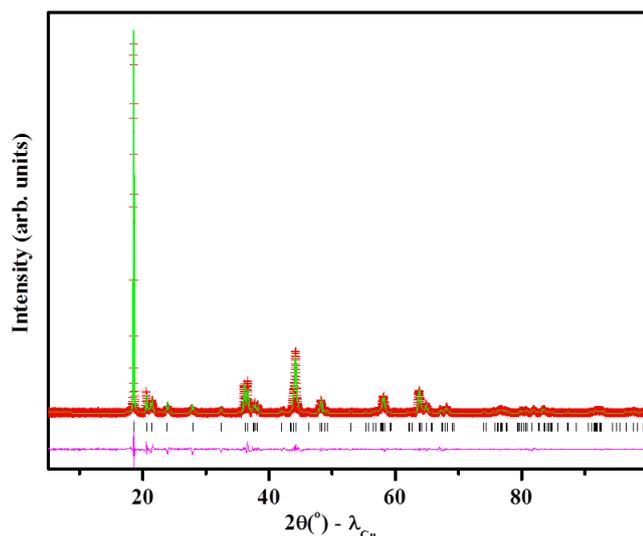
<sup>a</sup> Footnote text.

**Fig. 2** Caption Rietveld refinement of the structure of  $\text{Li}_3\text{MnRuO}_5$  from  
 5 PXRD data on the basis of  $\text{Li}_2\text{MnO}_3$  model. Observed (+), calculated (-)  
 and difference (bottom) profiles are shown. The vertical bars indicate  
 positions of the Bragg reflections

In the  $\text{Li}_2\text{MnO}_3$  structure (shown in Fig. 3) there are three  
 10 different Li positions, namely  $\text{Li}_{2b}$ ,  $\text{Li}_{2c}$  and  $\text{Li}_{4h}$  (the subscripts  
 represent corresponding Wyckoff sites) and a Mn position  
 ( $\text{Mn}_{4g}$ ).<sup>9</sup> Out of the three different lithium atoms,  $\text{Li}_{2c}$  and  $\text{Li}_{4h}$   
 along with oxygen build the sheets of  $\text{LiO}_6$  octahedra, while  $\text{Li}_{2b}$   
 and  $\text{Mn}_{4g}$  contribute for the sheets of  $\text{Li}_{0.33}\text{Mn}_{0.67}\text{O}_6$  octahedra  
 15 (sometimes referred as  $\text{LiMn}_2$  layer).


These two sheets of octahedra are stacked alternately along the  
 crystallographic  $c$ -direction of  $\text{Li}_2\text{MnO}_3$ . Our refinement for  
 $\text{Li}_3\text{MnRuO}_5$  indicates that  $\text{Li}_{2c}$  and  $\text{Li}_{4h}$  positions of  $\text{Li}_2\text{MnO}_3$  are  
 mainly occupied by lithium, with a small amount (~4%) of  
 20 mixing of transition metal ions at the 4h site (see Table 2). On the  
 other hand the  $\text{Li}_{2b}$  position of  $\text{Li}_2\text{MnO}_3$  in the  $\text{LiMn}_2$  layer is  
 partially occupied by both lithium and transition metal atoms (Mn  
 and Ru) with a ~58% occupancy of lithium (ideally 60%) and a  
 ~42%, (ideally 40%) by the transition metal atoms, Mn and Ru,  
 25 to the same extent. The  $\text{Mn}_{4g}$  site of  $\text{Li}_2\text{MnO}_3$  is mainly occupied  
 by an equal percentage of the transition metals (Mn and Ru),  
 ~48% each, and a small percentage, ~5%, by lithium. If we  
 ignore the slight admixture of atoms, we could write the structure  
 of  $\text{Li}_3\text{MnRuO}_5$  as  $\text{Li}[\text{Li}_{0.2}\text{Mn}_{0.4}\text{Ru}_{0.4}]\text{O}_2$  which compares with the  
 30  $\text{Li}[\text{Li}_{0.33}\text{Mn}_{0.67}]\text{O}_2$  model of  $\text{Li}_2\text{MnO}_3$ . Accordingly, the  $\text{LiO}_6$   
 octahedral sheets are the same in both structures, but the  
 alternating  $[\text{Li}_{0.33}\text{Mn}_{0.67}]$  sheets in  $\text{Li}_2\text{MnO}_3$  are replaced by  
 $[\text{Li}_{0.2}\text{Mn}_{0.4}\text{Ru}_{0.4}]$  sheets in  $\text{Li}_3\text{MnRuO}_5$ . As compared to  $\text{Li}_2\text{MnO}_3$ ,  
 $\text{Li}_3\text{MnRuO}_5$  shows an increase in the cell parameter as well as in  
 35 the average bond lengths of  $\text{Li/Mn/Ru-O}_6$  octahedra. The latter  
 could reflect the larger ionic radii of  $\text{Mn}^{3+}$  (0.645 Å) and  $\text{Ru}^{4+}$   
 (0.62 Å) (the likely oxidation states as revealed by XPS results,  
 see later) than  $\text{Mn}^{4+}$  (0.53 Å).

PXRD pattern of  $\text{Li}_3\text{FeRuO}_5$  also showed formation of single  
 40 phase with a similarity to the PXRD pattern of  $\text{LiCoO}_2$  (JCPDS  
 44-0145). Accordingly, we refined the PXRD data of  $\text{Li}_3\text{FeRuO}_5$   
 on the basis of the  $\text{LiCoO}_2$  ( $R-3m$ ) structural model.<sup>10</sup> The  
 refinement showed an almost ideal distribution of cations with a  
 small (~2%) mixing:  $[\text{Li}_{0.98}\text{Fe}_{0.01}\text{Ru}_{0.01}]_{3a}[\text{Li}_{0.22}\text{Fe}_{0.39}\text{Ru}_{0.39}]_{3b}\text{O}_2$ .

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

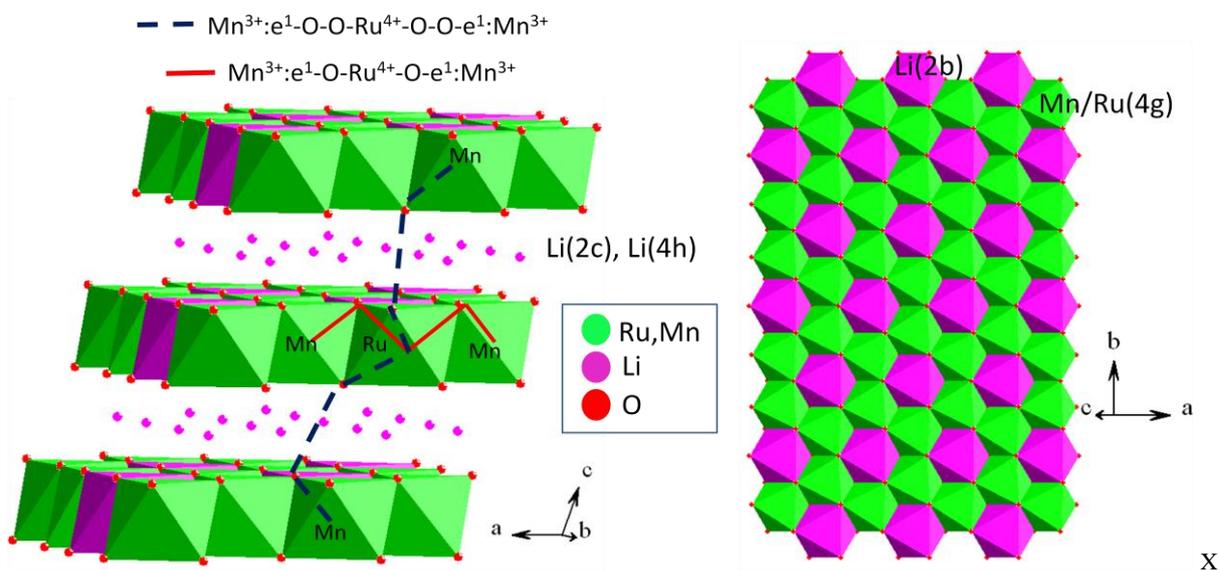

**Fig. 3** Crystal structure of  $\text{Li}_3\text{MnRuO}_5$  showing the  $\text{Li}_2\text{MnO}_3$  type structure. ( $\text{LiMn}_2$ ) layer is shown on the right. The analysis of the crystal structure of  $\text{Li}_3\text{MnRuO}_5$ , illustrating the different pathway through which superexchange interactions take place is depicted in the left hand side

5 Refined atomic coordinates and isotropic temperature factors are given in Table 4 and bond lengths in Table 5. Thus, the structure of  $\text{Li}_3\text{FeRuO}_5$  can be written as  $\text{Li}[\text{Li}_{0.2}\text{Fe}_{0.4}\text{Ru}_{0.4}]\text{O}_2$  if we ignore the slight admixture of atoms. The final Rietveld profile fit is shown in Fig. 4 and its crystal structure in Fig. 5. Though the  
 10 ionic radii of  $\text{Co}^{3+}$  (0.545 Å) and  $\text{Fe}^{3+}$  (0.55 Å) are similar in octahedral environment, the presence of bigger  $\text{Ru}^{4+}$  (0.62 Å) and

$\text{Li}^+$  (0.76 Å) in the mixed metal octahedral layers causes an increase in the cell parameters as well as in the average bond lengths as compared to the parent  $\text{LiCoO}_2$ .<sup>10, 11</sup> Both the  $\text{Li}(3a)\text{--O}$  (2.128 Å) and  $\text{Li/Fe/Ru}(3b)\text{--O}$  (2.036 Å) bonds are longer than the corresponding  $\text{Li}(3a)\text{--O}$  (2.092 Å) and  $\text{Co}(3b)\text{--O}$  (1.921 Å) bonds in  $\text{LiCoO}_2$ .<sup>10</sup>

20 **Table 4** Atomic coordinates and isotropic displacement parameters ( $U_{\text{iso}}$ ) for  $\text{Li}_3\text{FeRuO}_5$ . Space group  $R\text{-}3m$ ,  $a = 2.931(1)$  Å,  $c = 14.535(1)$  Å

Atom	site	x	y	z	$U_{\text{iso}}$	Occupancy
Li	3(a)	0	0	0	0.019(2)	0.981
Fe	3(a)	0	0	0	0.011(8)	0.013(1)
Ru	3(a)	0	0	0	0.011(8)	0.006(1)
Li	3(b)	0	0	0.5	0.019(2)	0.219
Fe	3(b)	0	0	0.5	0.027(1)	0.387(1)
Ru	3(b)	0	0	0.5	0.027(1)	0.394(1)
O	6(c)	0	0	0.245(1)	0.021(1)	1.0

Reliability Factors:  $R_p = 5.87$ ,  $R_{wp} = 7.95$ ,  $R_f^2 = 4.70$ ,  $\chi^2 = 1.58$

**Table 5** Bond distances (Å) and bond angles (°) for Li<sub>3</sub>FeRuO<sub>5</sub>


	Bond length / Å	BVS
Li/Fe/Ru(3a) – O	2.128(4)×6	Li: 1.00 ; Fe: 2.21; Ru: 2.71
Li/Fe/Ru(3b) – O	2.036(1)×6	Li: 1.29 ; Fe: 2.84 ; Ru: 3.48
Bond angle / °		
O(1) – Li/Fe/Ru(3a) – O(2)	87.06(1)	
O(1) – Li/Fe/Ru(3a) – O(3)	92.94(1)	
O(1) – Li/Fe/Ru(3b) – O(2)	92.06(1)	
O(1) – Li/Fe/Ru(3b) – O(3)	87.94(1)	

<sup>a</sup> Footnote text.

### Magnetic characterisation of pristine materials

Fig. 6 shows the evolution of the magnetic susceptibility with the temperature for Li<sub>3</sub>MnRuO<sub>5</sub>. It can be observed that the magnetic susceptibility obeys a Curie-Weiss law,  $\chi = 0.40/T+31.4$ , over a wide temperature range, i.e. 300-30 K. The calculated effective magnetic moment takes the value of 4.44  $\mu_B$ , which is smaller than the theoretical expected one, 5.62  $\mu_B$ , for this compound, where the oxidation states are Ru<sup>4+</sup> with low spin configuration  $t^4e^0$  and  $S=1$ ; while Mn<sup>3+</sup> with 3d<sup>4</sup> electronic configuration in octahedral coordination shows  $t^3e^1$  with  $S=2$ . This discrepancy could be due to the low spin configuration of Ru<sup>4+</sup>; the electrons are itinerant and therefore their contribution to the magnetic moment will be very weak. A similar behaviour has been reported by Goodenough et al.<sup>12</sup> in the study of the magnetic properties of ruthenium perovskites of composition La<sub>2</sub>MnRuO<sub>6</sub> where they indicated that the  $\pi$ -bonding 4d electrons of the low spin configuration of Ru<sup>4+</sup> are occupying itinerant-electron states of a  $\pi^*$ -band. As consequence of this, the magnetic moment is mainly due to the Mn<sup>3+</sup> ion. The negative value of -31.4 K of the Weiss constant is indicative of the onset of antiferromagnetic interactions. These antiferromagnetic interactions are fully confirmed from the net maximum found in the magnetic susceptibility at 9.4 K, see Figure 6.

In order to establish the origin of the divergence found between ZFC (zero field cooling) and FC (field cooling) magnetic susceptibility measurements below 9.4 K, magnetization as a function of the magnetic field has been performed at 4, 8 and 50 K and the hysteresis curve was measured at 4 K (Figure 7). A linear behaviour is observed above and below the critical temperature that agrees well with the antiferromagnetic behaviour proposed for the Li<sub>3</sub>MnRuO<sub>5</sub> compound, where any metamagnetic transition is not observed below 5 T. The magnetic hysteresis loop obtained at 4 K (see Figure 7) indicates the absence of spin glass behaviour that will be rise a larger values of the FC magnetization than the ZFC data as a consequence of the freezing of the induced moment by the magnetic field. The weak ferromagnetic component arises from the canting of the Ru-Mn sublattices which are antiferromagnetically ordered through the superexchange pathways describe below.

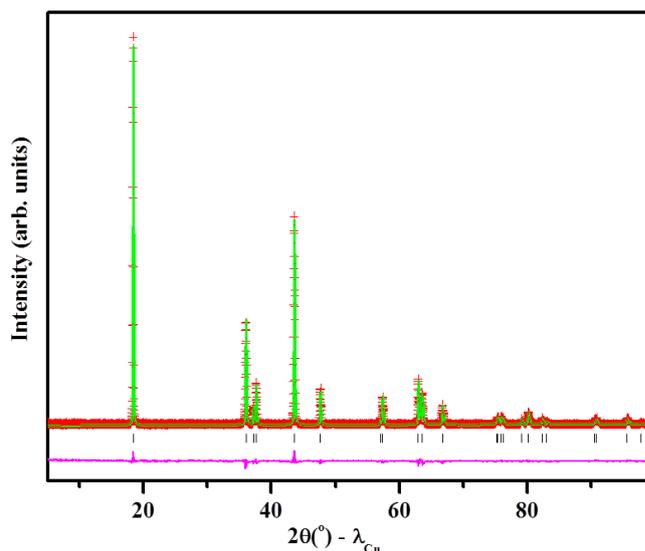


**Fig.4** Rietveld refinement of the structure of Li<sub>3</sub>FeRuO<sub>5</sub> from PXRD data on the basis of LiCoO<sub>2</sub> model. Observed (+), calculated (-) and difference (bottom) profiles are shown. The vertical bars indicate positions of the Bragg reflections



The analysis of the crystal structure of Li<sub>3</sub>MnRuO<sub>5</sub>, is very illustrative to establish the different pathways through which of these superexchange interactions take place (see Fig. 3). In this sense, in the *ab*-plane the antiferromagnetic superexchange interactions within the Ru-Mn layers following the pathway Mn<sup>3+</sup>:e<sup>1</sup>-O-Ru<sup>4+</sup>-O-e<sup>1</sup>:Mn<sup>3+</sup> should be stronger than the weak ferromagnetic ones expected for the Mn<sup>3+</sup>:e<sup>1</sup>-O-e<sup>1</sup>:Ru<sup>4+</sup> because of  $\pi$ -itinerant electrons of the Ru<sup>4+</sup>. Along the *c*-axis the pathway of the type Mn<sup>3+</sup>:e<sup>1</sup>-O-O-Ru<sup>4+</sup>-O-O-e<sup>1</sup>:Mn<sup>3+</sup> yields weak antiferromagnetic superexchange interactions. Both the low values of the Weiss constant and the estimated Neel temperature which are -33.4 K and 9.4 K, respectively, agree well with the weakness of these antiferromagnetic interactions that take place through the pathways mentioned above.

In the case of the Li<sub>3</sub>FeRuO<sub>5</sub> the magnetic susceptibility (not shown) exhibits a broad maximum around 300 K and a

pronounced irreversibility between the FC and ZFC susceptibility data that could be due to the presence of a ferromagnetic component arising from some iron oxide impurity not detected from XRD data. However, at low temperature the onset of a net maximum at 20 K was observed, which as in the case of the analogous manganese compound could be due to the presence of weak antiferromagnetic interactions.

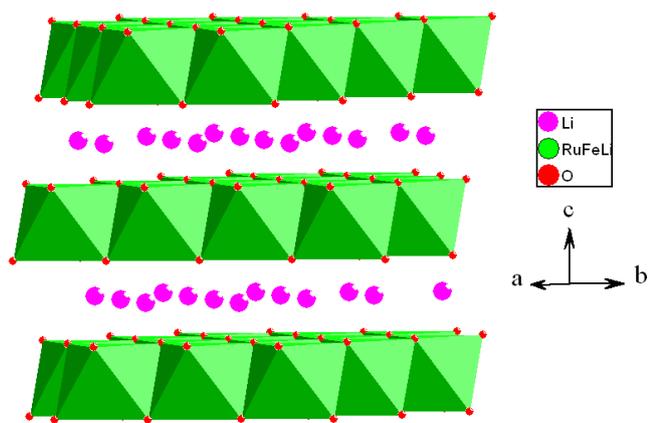

10 **Fig. 5** Crystal structure of  $\text{Li}_3\text{FeRuO}_5$ . For clarity,  $\text{LiO}_6$  octahedra are omitted

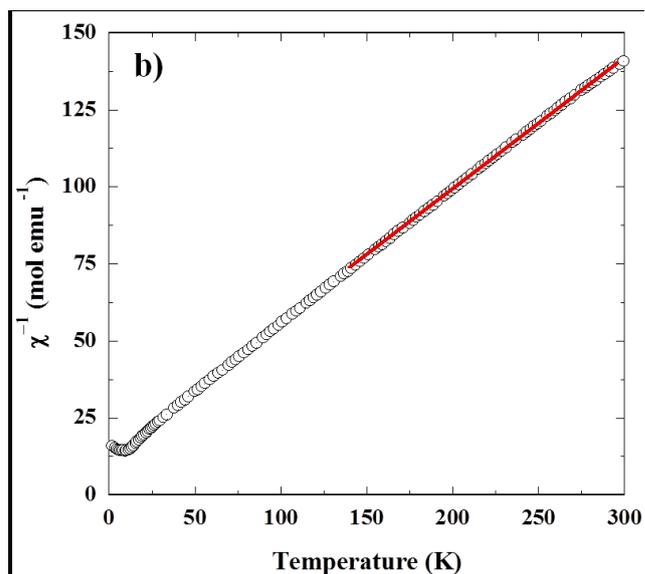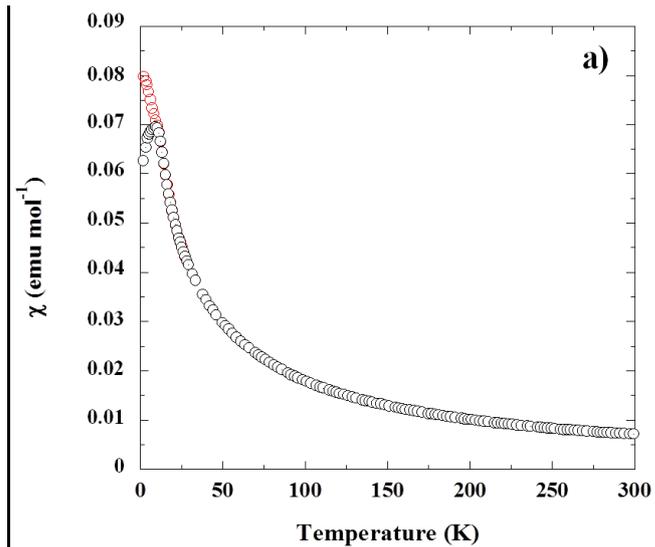

35 **Fig. 6** a) Field cooling (red circles) and zero field cooling (black circles) magnetic susceptibility temperature dependence of  $\text{Li}_3\text{MnRuO}_5$ , b)  $\chi^{-1}$  vs. T plot

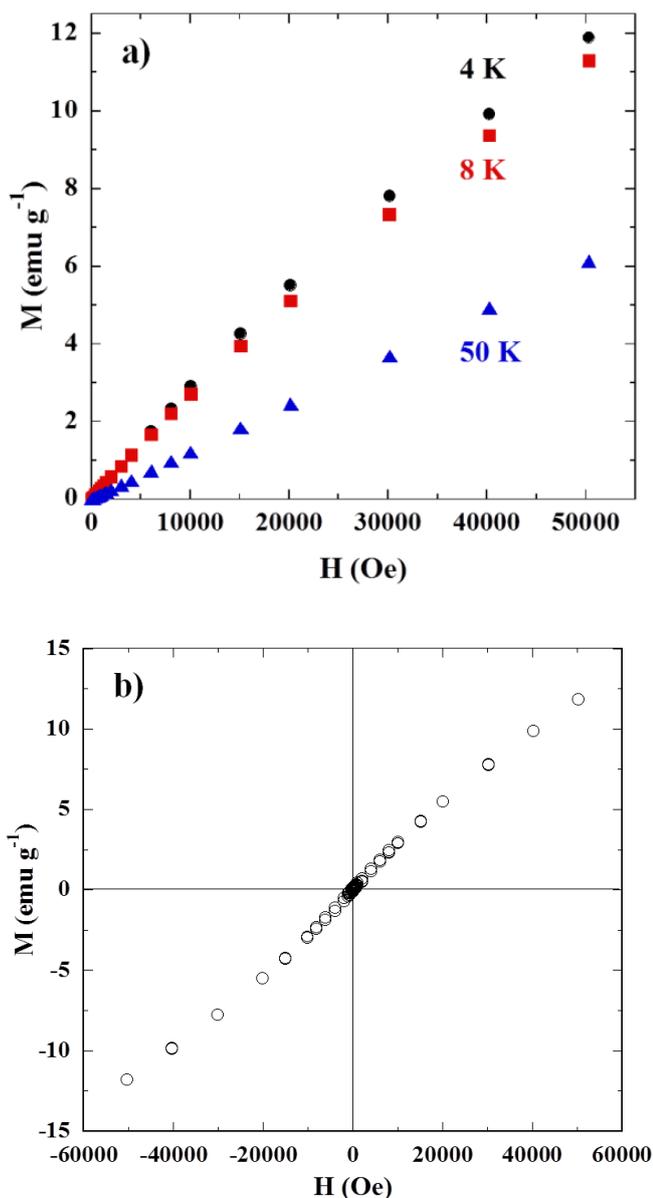


Fig. 7 a) Magnetization as a function of the magnetic field at 4, 8 and 50 K and b) the hysteresis curve measured at 4 K.

### XPS of pristine materials

X-ray photoelectron spectroscopy (XPS) measurements were carried out on the pristine Li<sub>3</sub>MRuO<sub>5</sub> (M = Mn and Fe) oxides to determine the oxidation states of the metal atoms. The core level Ru 3d spectra exhibits Ru 3d<sub>5/2</sub> binding energies (BE) around 282.0 and 281.8 eV for Li<sub>3</sub>MnRuO<sub>5</sub> and Li<sub>3</sub>FeRuO<sub>5</sub>, respectively (Figures 8a and 9a and Table 6). In both oxides, the oxidation state of ruthenium corresponds to Ru<sup>4+</sup>.<sup>13</sup> The core level spectrum of Mn 2p<sub>3/2</sub> in pristine Li<sub>3</sub>MnRuO<sub>5</sub> shows a peak maximum at around 641.8 eV (Figure 8b and Table 6) which corresponds to Mn<sup>3+</sup>.<sup>14</sup> The core level peak of Fe 2p<sub>3/2</sub> of Li<sub>3</sub>FeRuO<sub>5</sub> appears at around 710.3 eV (Figure 9b and Table 6) which can be attributed to Fe<sup>3+</sup>.<sup>15</sup> On the other hand, O 1s core level spectra in the pristine samples exhibit two maxima each. The first peak (529.5 and

529.3 eV in Li<sub>3</sub>MnRuO<sub>5</sub> and Li<sub>3</sub>FeRuO<sub>5</sub>, respectively) in each spectrum corresponds to O<sup>2-</sup> anions in a crystalline network and the second one, 531.4 eV in both samples (Figures 8c and 9c and Table 6), belongs to weakly adsorbed surface oxygen species.<sup>16, 17</sup>

From the results, we formulate the pristine oxides as Li<sub>3</sub>M<sup>3+</sup>Ru<sup>4+</sup>O<sub>5</sub> (M = Mn and Fe).

### Electrochemical behavior

#### Li<sub>3</sub>MnRuO<sub>5</sub>

Figure 10 shows the first two charge-discharge cycles of Li<sub>3</sub>MnRuO<sub>5</sub> in the 3.0 to 4.5 V voltage range.

For Li<sub>3</sub>MnRuO<sub>5</sub>, an initial sloping region followed by a long plateau developing a total large capacity in the first charge (ca. 240 mAhg<sup>-1</sup>) can be seen. The corresponding equivalent quantity of de-inserted lithium, ca. 2.3 Li/f.u., deserves attention, because it is higher than that expected for oxidation of Mn<sup>3+</sup> to Mn<sup>4+</sup> and Ru<sup>4+</sup> to Ru<sup>5+</sup>. The general behaviour is similar to that reported for Li-rich layered Li[Li<sub>1-x</sub>M<sub>x</sub>]O<sub>2</sub> oxides, in particular the solid solution Li<sub>2</sub>MnO<sub>3</sub>-LiMO<sub>2</sub> (M= Ni, Co, Cr<sup>18-28</sup>). We observed a similar electrochemical behaviour in other members of the Li<sub>3</sub>MRuO<sub>5</sub> series (M= Co or Ni) as well.<sup>3</sup> According to the structural characterisation above presented, Li<sub>3</sub>MnRuO<sub>5</sub> can be expressed in fact as Li[Li<sub>0.2</sub>Mn<sub>0.4</sub>Ru<sub>0.4</sub>]O<sub>2</sub> being isostructural to Li<sub>2</sub>MnO<sub>3</sub>.

A significant amount of lithium ions (ca. 1.0 Li/f.u, 105 mAh/g) are de-inserted in the 3.0 - 4.25 V voltage range. According to the voltage profile in this region, it seems that more than one process are involved, both of them being ruled by solid solution formation. Considering the formula Li<sub>3</sub>Mn<sup>3+</sup>Ru<sup>4+</sup>O<sub>5</sub>, which has been proposed in view of magnetic and XPS characterization, the incomplete oxidation of both Mn<sup>3+</sup> and Ru<sup>4+</sup> to Mn<sup>4+</sup> and Ru<sup>5+</sup>, respectively, accounts for the partial de-insertion of lithium ions in this voltage region. Interestingly, the case is different from that recently reported for the solid solution Li<sub>2</sub>MnO<sub>3</sub>-Li<sub>2</sub>RuO<sub>3</sub> where Ru<sup>4+</sup> and Mn<sup>4+</sup> are present and therefore only Ru<sup>4+</sup> is active upon oxidation in this voltage range.


The presence of the two processes in Li<sub>3</sub>Mn<sup>3+</sup>Ru<sup>4+</sup>O<sub>5</sub> is clearly seen in the voltammogram shown in Figure 10b. In the first oxidation wave, two peaks at 3.8 and 4.1 V are clearly seen. These peaks can be assigned to Ru<sup>4+</sup>/Ru<sup>5+</sup> and Mn<sup>3+</sup>/Mn<sup>4+</sup> redox pairs, respectively, taking into account previous results on very related oxides. For example, Ru<sup>4+</sup> to Ru<sup>5+</sup> oxidations have been found to occur at 3.6 V in the very related cases of Li<sub>2</sub>Ru<sub>1-x</sub>M<sub>x</sub>O<sub>3</sub> (M = Mn or Sn).<sup>19, 20</sup> The Mn<sup>3+</sup> to Mn<sup>4+</sup> oxidation process has been reported to occur at 4.0 V in LiMn<sub>2</sub>O<sub>4</sub>.<sup>29-31</sup> Interestingly, the corresponding reduction peaks are clearly observed at 3.43 and 4.09 V. The almost negligible polarization of the high voltage peak at ca. 4 V seems to indicate that other processes may be occurring in the same voltage region, probably participated by modification of the oxygen deposited species after electrolyte oxidation in the first oxidation and masking the corresponding peaks. Note that the reduction peak at 4.09 is very broad and flattened so that maximum is difficult to assign.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

**Table 6** XPS data for  $\text{Li}_3\text{MRuO}_5$ , M = Mn and Fe at different oxidation stages.

$\text{Li}_3\text{MRuO}_5$	Conditions	Ru ( $3d_{5/2}$ ) (eV)	M ( $2p_{3/2}$ ) (eV)
	Pristine	282.0	641.8
M = Mn	Oxidized up to 4.15 V	282.4	642.2
	Oxidized up to 4.50 V	282.7	643.0
M = Fe	Pristine	281.8	710.3
	Oxidized up to 3.80 V	282.9	709.2
	Oxidized up to 4.50 V	283.0	--
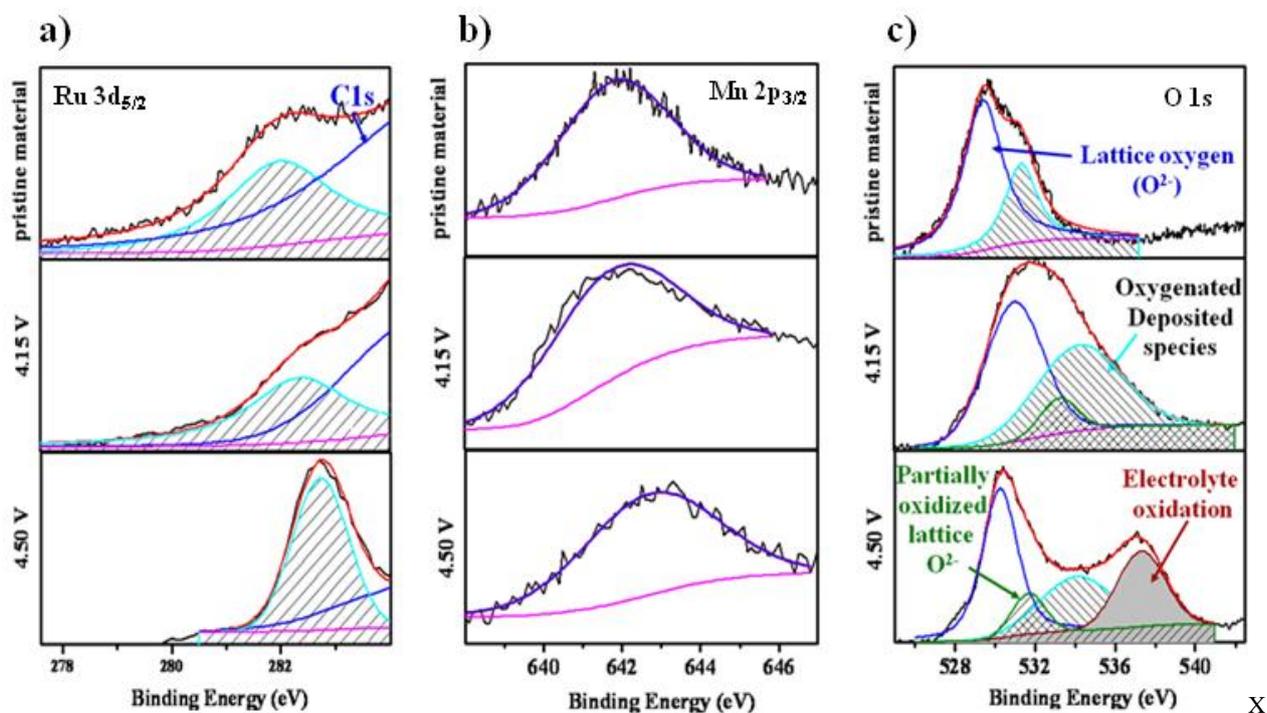
<sup>a</sup> Footnote text.

5 **Fig. 8** Comparison of XPS data for pristine, 4.15 V and 4.50 V oxidized  $\text{Li}_3\text{MnRuO}_5$  samples. (a) Ru 3d spectra (b) Mn 2p spectra and (c) O 1s spectra.

At even higher voltage, another well differentiated region is observed between 4.25 and 4.4 V, according to voltage profile. A large plateau indicates the occurrence of a new electrochemical process which is evidenced in the voltammogram shown in Fig.

10 10b, where a high oxidative current develops an incomplete peak at high voltage.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxxx

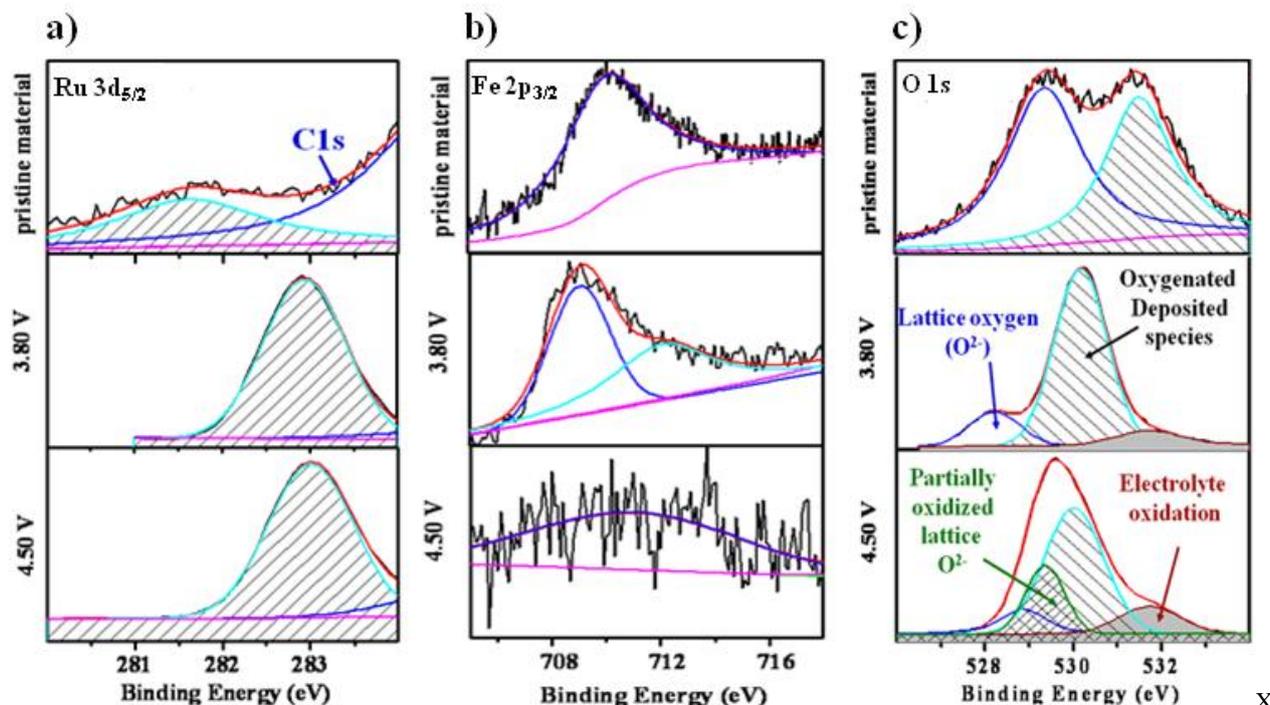



Fig. 9 Comparison of XPS data for pristine, 3.80 V and 4.50 V oxidized  $\text{Li}_3\text{FeRuO}_5$  samples. (a) Ru 3d spectra (b) Mn 2p spectra and (c) O 1s spectra.

Much of the capacity developed during the first charge corresponds to this region in which ca. 1.3 Li ions seems to be de-inserted. Such a large amount of lithium may correspond to oxidation of  $\text{Mn}^{3+}$  or  $\text{Ru}^{4+}$  to high valence states, 5+ and 6+, respectively. In view of the high polarizing power of these cations, related to an increasing covalency of the M-O bond, another scenario involving the oxidation of lattice  $\text{O}^{2-}$  to  $\text{O}^-$  can be proposed. In this connection, the oxidation of the ligand, oxide ion, to  $\text{O}^-$ , has been reported in the closely related oxide  $\text{Li}_2\text{Ru}_{0.5}\text{Mn}_{0.5}\text{O}_3$ .<sup>19</sup> The participation of the ligands in the redox chemistry was even early proposed in the deep de-lithiation of  $\text{LiCoO}_2$  to  $\text{CoO}_2$ .<sup>32</sup> However, the oxidation of  $\text{O}^{2-}$  ligand involves oxygen evolution as a typical characteristic of lithium rich layered transition metal oxides of the solid solution  $\text{Li}_2\text{MnO}_3$ - $\text{LiMO}_2$  where high valent cations are formed on oxidation.<sup>21, 23, 28</sup>

To address the redox process involved in the deinsertion of lithium from  $\text{Li}_3\text{MnRuO}_5$ , XPS measurements were performed on both samples oxidized to two different voltages. The spectra for pristine  $\text{Li}_3\text{MnRuO}_5$  above described and for samples charged up to 4.15 V and 4.50 V are shown in Figure 8 and Table 6. The Ru  $3d_{5/2}$  core level spectrum which shows a binding energy ~282.0 eV for pristine  $\text{Li}_3\text{MnRuO}_5$ , consistent with  $\text{Ru}^{4+}$ ,<sup>13</sup> shifts positive to 282.4 eV in sample oxidized at 4.15V (Figure 8a and Table 6). This positive shift indicates likely oxidation of  $\text{Ru}^{4+}$  to  $\text{Ru}^{5+}$  in this oxidized sample. Electrochemical data showed that

oxidation of  $\text{Ru}^{4+}$  and  $\text{Mn}^{3+}$  in the low voltage region (3-4.25 V) was not completed. Thus, we also investigated the characteristic of the Ru  $3d_{5/2}$  core level spectrum in the sample oxidized at 4.50 V. As expected, it can be seen an additional positive shift to 282.7 eV indicative of further oxidation of  $\text{Ru}^{4+}$  above 4.15 V. The situation is similar regarding Mn; the core level spectrum of Mn  $2p_{3/2}$  in the pristine  $\text{Li}_3\text{MnRuO}_5$  shows a peak maximum around 641.8 eV, which corresponds to  $\text{Mn}^{3+}$  (Figure 8b and Table 6).<sup>14</sup> When the  $\text{Li}_3\text{MnRuO}_5$  electrode is charged up to 4.15 V, the Mn  $2p_{3/2}$  binding energy shifts positive to 642.2 eV and later to 643.0 eV at 4.50 V, suggesting an oxidation of  $\text{Mn}^{3+}$  to  $\text{Mn}^{4+}$  (Figure 8b and Table 4).<sup>14</sup> Pristine  $\text{Li}_3\text{MnRuO}_5$  shows two peaks for O 1s, first one at 529.5 eV (lattice oxide ion,  $\text{O}^{2-}$ ) and 531.4 eV (weakly adsorbed surface species).<sup>16, 33</sup> In the charged materials, the intensity and the area under the peak at ~531.4 eV increases. A new feature at ~537.3 eV appears, which likely corresponds to electrolyte oxidation.<sup>17, 33</sup> In the 4.50 V oxidized material, a new component around 531.6 eV appears and this is likely to be due to partially oxidized lattice oxide (with a lower electron density as compared to  $\text{O}^{2-}$  in the pristine material) (Figure 8c).<sup>33</sup> The results indicate a progressive oxidation of the transition metals to  $\text{Mn}^{4+}$  and  $\text{Ru}^{5+}$ . At 4.15 V, metal oxidation has not been completed yet as expected from the electrochemical curve while partial electrolyte oxidation has started. At some point below 4.50 V, the ideal composition  $\text{LiMn}^{4+}\text{Ru}^{5+}\text{O}_5$  in the fully charged state is reached, while extra capacity is developed due to oxide lattice oxidation.

Now, paying attention to the discharge, it can be seen that capacity drops and voltage profile is more similar to those of the region in which oxidation of Mn and Ru occurs though a high voltage contribution is observed. Second charge parallels the voltage profile of the discharge showing the reversibility onwards.

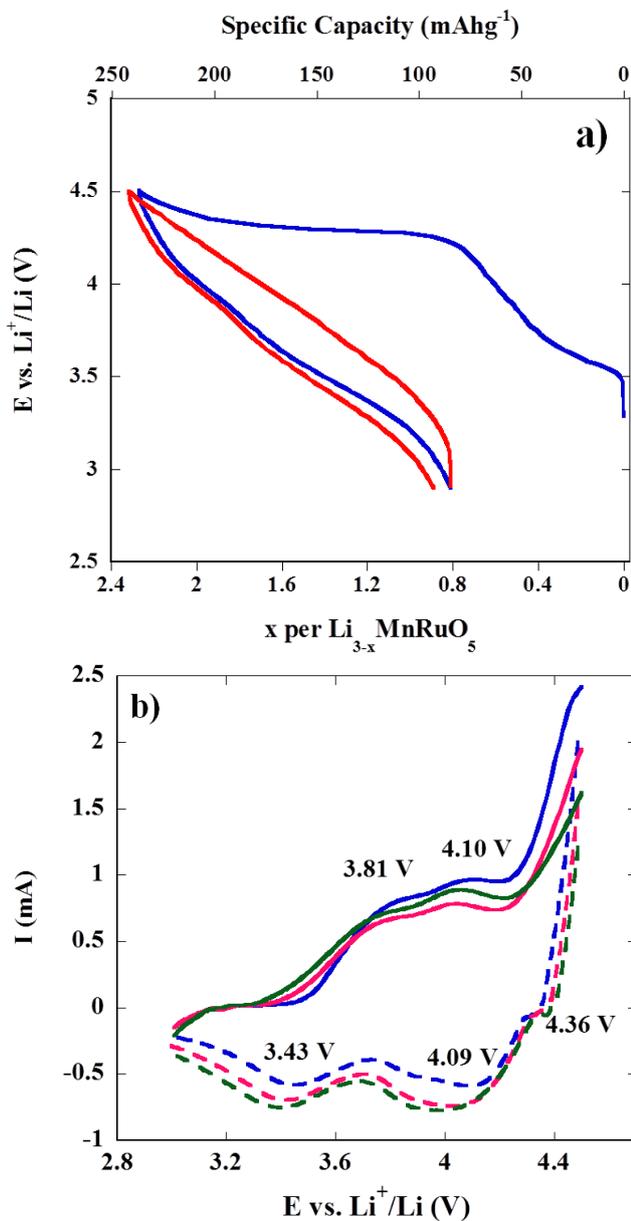

**Fig. 10** a) Typical voltage-composition/capacity plot showing first (blue) and second (red) charge-discharge cycles of cell bearing  $\text{Li}_3\text{MnRuO}_5$  as the active material. b) Stepped-potential chronoamperometry plot of  $\text{Li}_3\text{MnRuO}_5$  electrode (10 mV/h). Oxidation and corresponding reduction cycles are plotted in continuous and dashed line, respectively.

Thus, we note that the reversible capacity (ca. 160  $\text{mAhg}^{-1}$ , 1.55 Li p.f.u.) observed after the first charge is not only due to  $\text{Mn}^{4+}$  and  $\text{Ru}^{5+}$  reduction/oxidation (only ca. 1.0 Li/f.u., 105  $\text{mAhg}^{-1}$  were ascribed to these cations on the first charge in the 3.0 - 4.25 V voltage range) but also to a reversible contribution at high voltage of the  $\text{O}^- / \text{O}^{2-}$  redox couple. The voltammogram shown in Fig. 10b shows that after the first oxidative wave, the high

current observed at high voltage ascribed to the  $\text{O}^- / \text{O}^{2-}$  redox couple, decreases considerably while in the reductive wave, the oxide ion related process is observed as a peak of current at 4.36 V that keeps the same current in the three cycles shown.

However, it seems clear from the voltage profile that the two phase transformation taking place during the long plateau of the first charge is not reversible. This can be due to a significant irreversible loss of oxygen that is associated with oxygen vacancies and structural reorganization as it has been proved in the case of  $\text{Li}_2\text{Ru}_{1-y}\text{Sn}_y\text{O}_3$ . In the latter, oxygen evolution is partially inhibited by the presence of Sn facilitating the condensation of  $\text{O}^-$  to  $\text{O}_2^{2-}$  and hence favouring reversibility.<sup>20</sup>

### $\text{Li}_3\text{FeRuO}_5$


Figure 11a shows the first two charge-discharge cycles of  $\text{Li}_3\text{MnRuO}_5$  in the 3.0 to 4.5 V voltage range. The behavior resembles the one described for the Mn analog inasmuch as a long charge process (ca. 144  $\text{mAhg}^{-1}$ , 1.38 Li/f.u.), in which at least three voltage-composition regions are distinguished, is followed by a sloping reversible discharge shorter than first charge. In the beginning of the first charge, a sloping region between 3.0 and 4.0 V can be identified in the voltage-composition curve. The process is clearly defined at 3.7 V in the voltammogram of Fig. 11b. The potential indicates that in this voltage region  $\text{Ru}^{4+}$  is being oxidized.

The capacity developed in this region (ca. 50  $\text{mAhg}^{-1}$ ) is half of that in the case of Mn compound and corresponds to ca. 0.45 Li/f.u. Note that according to XPS characterisation, the pristine material can be expressed as  $\text{Li}_3\text{Fe}^{3+}\text{Ru}^{4+}\text{O}_5$ . As in the case of  $\text{Li}_3\text{MnRuO}_5$ , oxidation of  $\text{Ru}^{4+}$  is not completed at this stage. Besides, the second electroactive metal is now  $\text{Fe}^{3+}$  which is not expected to be oxidized at such low voltage.

A large capacity process occurs above 4.0 V involving a long plateau at ca. 4.2 V. Similarly to the case of Mn, we could ascribe this to the oxidation of oxide ions. The oxidative process is detected also in voltammogram shown in Fig. 11b as a broad peak at 4.26 V. Finally at ca. 4.5 V, another process is detected in the voltage-composition curve (Fig. 11a). Whether it is related with the electrolyte catalyzed oxidation due to the presence of an impurity no detectable by conventional XRD remains unknown. Note that magnetic measurement detected the presence of a small amount of strongly ferromagnetic impurity. We also noted that the extension and appearance of this process depends somehow on the batch. For example in the experiment shown in Fig. 11b this high voltage process is not detected. However, the oxidation of  $\text{Fe}^{3+}$  in  $\text{Li}_3\text{Fe}^{3+}\text{Ru}^{4+}\text{O}_5$  is discarded since it is expected at much higher voltage according to previous results on related materials (ca. 5.1 V<sup>34</sup>). In any case we discarded also this possibility based on XPS experiments (see below).

On discharge, again similarly to the Mn case, a sloping discharge shorter than charge and partially reversible can be seen (Fig. 11a). After first charge, the capacity is mainly due to the  $\text{Ru}^{5+}/\text{Ru}^{4+}$  redox couple, but with participation of  $\text{O}^-/\text{O}^{2-}$  as indicated by the maxima of negative current located at 4.10 V (Fig. 11b). Thus, oxidation of  $\text{O}^{2-}$  seems to be also reversible to some extent.

On the other hand, we did not investigate oxidation of  $\text{Fe}^{3+}$  at ~50 V, due to the instability of the electrolyte at such high voltage.

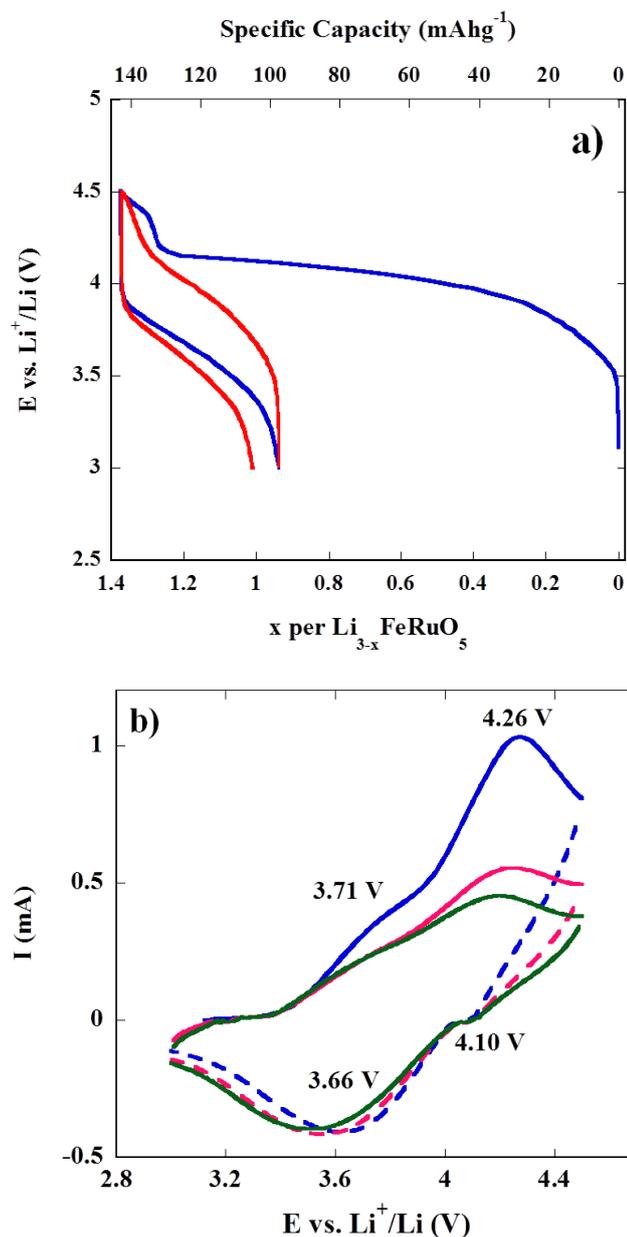


**Fig. 11** a) Typical voltage-composition/capacity plot showing first (blue) and second (red) charge - discharge cycles of cell bearing  $\text{Li}_3\text{FeRuO}_5$  as the active material. b) Stepped-potential chronoamperometry plot of  $\text{Li}_3\text{FeRuO}_5$  electrode (10 mV/h). Oxidation and corresponding reduction cycles are plotted in continuous and dashed line, respectively

To confirm this interpretation of the electrochemical behaviour of  $\text{Li}_3\text{FeRuO}_5$ , we recorded XPS spectra for samples charged up to 3.80 V and 4.50 V. Data are shown in Figure 9 and Table 6 together with those of pristine  $\text{Li}_3\text{FeRuO}_5$ . The core level spectrum of Ru  $3d_{5/2}$  in  $\text{Li}_3\text{FeRuO}_5$ , shifts positive by more than 1 eV, from 281.8 in the pristine material to 282.9 eV, when oxidized up to 3.80 V. This shift reveals that  $\text{Ru}^{4+}$  is oxidized to higher oxidation states (Figure 9a and Table 6). A further, but very small, shift to 283.0 eV when oxidized at 4.50 V indicates that oxidation of  $\text{Ru}^{4+}$  mainly occurs below 3.8 V. Note that the

corresponding process was observed by electrochemical methods close to 3.6 V and that capacity indicated that oxidation of  $\text{Ru}^{4+}$  was not completed at 4.0 V. Fe  $2p_{3/2}$  core spectrum, which occurs at 710.3 eV, corresponding to  $\text{Fe}^{3+}$ ,<sup>15</sup> in the pristine material shifts negative to 709.2 eV upon oxidation to 3.8 V and a weak satellite appears around 712.2 eV, besides. When oxidized to 4.50 V, no clear peak is observed. Both effects could result from a modification of the oxygen ligands around iron inducing strong electronic redistributions in the Fe-O bonds. A similar explanation has been given by Sathiya et.al.<sup>17</sup> Nevertheless, we may discard oxidation of  $\text{Fe}^{3+}$  below 4.5 V. The O 1s spectrum for the pristine  $\text{Li}_3\text{FeRuO}_5$  exhibits the two well resolved characteristic features at 529.3 eV and 531.4 eV, corresponding to lattice oxide,  $\text{O}^{2-}$ , as previously described.<sup>16, 33</sup> As the pristine  $\text{Li}_3\text{FeRuO}_5$  is charged to 3.80 V, the peaks shift negative and a new feature appears at around 531.7 eV due to electrolyte oxidation.<sup>17, 33</sup> On further oxidation to 4.50 V, a new peak around 529.4 eV comes into picture, corresponding to oxidized  $\text{O}^{2-}$  ions as in the case of  $\text{Li}_3\text{MnRuO}_5$ .<sup>33</sup> The results reveal that  $\text{Ru}^{4+}$  is definitely getting oxidized to  $\text{Ru}^{5+}$  in the samples charged to 3.80 V though we do not have a conclusive evidence of the oxidation state of iron and oxygen in the oxidized samples. It is most likely that iron remains in the  $\text{Fe}^{3+}$  state with a reorganization of oxygen accompanying the oxygen release due to oxidation of part of oxide ions.

#### Cycling behavior of $\text{Li}_3\text{MRuO}_5$

The first charge capacity is developed through the partial oxidation of both  $\text{Mn}^{3+}$  and  $\text{Ru}^{4+}$  for  $\text{M} = \text{Mn}$  and  $\text{Ru}^{4+}$  for  $\text{M} = \text{Fe}$  compound, followed by the partial oxidation of  $\text{O}^{2-}$  to  $\text{O}^-$  ions. On discharge, electrochemical characterisation suggests that the above mentioned cations are reduced as well as  $\text{O}^-$  at least partially. Similar partial reversible behaviour of the  $\text{O}^{2-}/\text{O}^-$  redox couple has been previously shown in very related layered compounds such as  $\text{Li}_2\text{Ru}_{1-y}\text{Mn}_y\text{O}_3$ <sup>19, 20</sup> and  $\text{Li}_2\text{Ru}_{1-y}\text{Sn}_y\text{O}_3$ .<sup>16</sup> We also proposed a role of this redox couple in the electrochemical behavior of other members of the  $\text{Li}_3\text{MRuO}_5$  family ( $\text{M} = \text{Co}$  and  $\text{Ni}$ ) that behaves quite similarly.<sup>3</sup> However, long cycling behaviour is found to be limited in all the  $\text{Li}_3\text{MRuO}_5$  investigated compounds. After first charge, reversibility is observed and capacity is well kept (Figure 12) but just for a few cycles The figure shows the last cycle number before electrical failure occurs as a characteristic of every cell when cycling these materials up to 4.50 V. We believe that contrarily to that observed for related systems where long life cycling was achieved with the participation of a reversible anionic redox system,<sup>19-21</sup> in the case of the  $\text{Li}_3\text{RuMO}_5$  series, oxygen evolution is likely not inhibited by reorganization of oxygen environments based on the formation of  $\text{O}_2^{2-}$  as in other systems. In fact, if the participation of the  $\text{O}^{2-}$  ligand in the redox process is minimised by cycling  $\text{Li}_3\text{RuMO}_5$  in narrower voltage range, cyclability is very much improved. Compare for example data corresponding to  $\text{M} = \text{Mn}$  cycled up to 4.15 and 4.50 V depicted in Fig. 12. At this lower cut-off voltage, the cycling is improved and cell life is longer with very good capacity retention, albeit lower capacity is reached due the shortening of the voltage range.

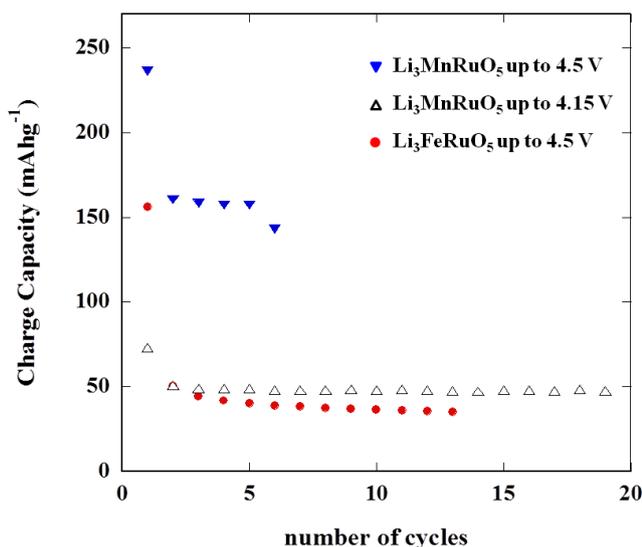

**Fig 12** Charge capacity variation with cycle number for  $\text{Li}_3\text{RuMO}_5$  ( $M = \text{Mn}$  and  $\text{Fe}$ ) in the 3.0 - 4.5 V voltage range. In the case of  $\text{Li}_3\text{RuMnO}_5$  cycling in the 3.0 and 4.15 V range is also shown

## 5 Conclusions

New lithium-rich layered oxides with composition  $\text{Li}_3\text{MRuO}_5$  ( $M = \text{Mn}$ ,  $\text{Fe}$  and  $\text{Cu}$ ) have been synthesized for the first time. Crystal structure, magnetic properties, and lithium deinsertion/insertion electrochemistry have been investigated for  $M = \text{Mn}$  and  $\text{Fe}$ .  $\text{Li}_3\text{MRuO}_5$  is related to  $\text{Li}_2\text{MnO}_3$  ( $C2/m$ ) and  $\text{LiCoO}_2$  ( $R-3m$ ). In both structures,  $\text{Li}$  and ( $\text{Li}_{0.2}\text{M}_{0.4}\text{Ru}_{0.4}$ ) layers are stacked alternately along the  $c$ -axis. Magnetic measurements indicate the presence of  $\text{Mn}^{3+}$  and low spin configuration for  $\text{Ru}^{4+}$  in  $\text{Li}_3\text{MnRuO}_5$ , where the  $\text{Ru}^{4+}$  itinerant electrons are occupying a  $\pi^*$ -band. The onset of a net maximum in the  $\chi$  vs.  $T$  plot at 9.5 K and the negative value of the Weiss constant ( $\theta$ ) of -31.4 K indicate the presence of antiferromagnetic superexchange interactions according to different pathways. The  $\text{Fe}$  analogue oxide may have the same behaviour at low temperature since the onset of a net maximum at 20 K has been observed as in the case of the analogous manganese compound. Lithium electrochemical studies show a similar behaviour for both oxides and related to other  $\text{Li}$ -rich layered oxides in general. In both cases, a long first charge is observed. The corresponding capacities (240  $\text{mAhg}^{-1}$ , 2.3  $\text{Li/f.u.}$  and 144  $\text{mAhg}^{-1}$ , 1.38  $\text{Li/f.u.}$  for  $M = \text{Mn}$  and  $\text{Fe}$ , respectively) indicate that not only the transition metals are participating in the *redox* chemistry. An initial sloping region (OCV ca. 4.1 V) is followed by a long *plateau* (ca. 4.3 V). Further discharge-charge cycling points to partial reversibility (ca. 160 and 45  $\text{mAhg}^{-1}$  for  $\text{Mn}$  and  $\text{Fe}$ , respectively). XPS characterisation of both the pristine and electrochemically oxidized  $\text{Li}_3\text{MnRuO}_5$  samples reveals that  $\text{Mn}^{3+}$  and  $\text{Ru}^{4+}$  are partially oxidized to  $\text{Mn}^{4+}$  and  $\text{Ru}^{5+}$  in the sloping region at low voltage, while in the long *plateau*  $\text{O}^{2-}$  is also oxidized to  $\text{O}^-$  related species. Oxygen release likely occurs and it is pointed out that this could be the origin of cells' failure on cycling. In  $\text{Li}_3\text{FeRuO}_5$  the oxidation process appears to affect only  $\text{Ru}^{4+}$  (sloping region) and  $\text{O}^{2-}$  (*plateau*), while  $\text{Fe}$  seems to retain its  $3+$  state.

Cycling life of cells is short in both cases, because, cell failure is observed just after few cycles in the 3.0-4.5 V range. It seems then that accommodation of oxidized oxygen species in  $\text{Li}_3\text{MRuO}_5$  is neither favoured in the  $\text{LiCoO}_2$  structure of  $\text{Li}_3\text{FeRuO}_5$  nor in the  $\text{Li}_2\text{MnO}_3$  structure of  $\text{Li}_3\text{MnRuO}_5$ , resulting in poor cycling behaviour. Interestingly,  $\text{Li}$ -rich layered oxides such as  $\text{Li}_2\text{Ru}_{1-y}\text{Sn}_y\text{O}_3$  have been reported in the literature to cycle better even with the participation of  $\text{O}^{2-}$  ligand in the reversible *redox* process.

## Acknowledgements

The authors are indebted to the Spanish Ministerio de Ciencia e Innovación (MICINN, Dirección General de Cooperación Internacional) for awarding and funding the Joint project ACI2009-0972 which made possible this work. Partial financial support coming from projects MAT2010-19837-C06, MAT2013-46452-C4-1-R, MAT2010-19460 (MICINN) and from the program S2009/PPQ-1626 (Comunidad de Madrid) is also acknowledged. On the other hand, J.G. and S.N. thank the Department of Science and Technology, Govt. of India for the award of Indo-Spanish project and Ramanna Fellowship.

## Notes and references

- <sup>a</sup> Solid State and Structural Chemistry Unit, Indian Institute of Science, Bangalore 560012, India. E-mail: gopal@sscu.iisc.ernet.in
- <sup>b</sup> Departamento de Química Inorgánica, Facultad de Ciencias Químicas, Universidad Complutense de Madrid, 28040 Madrid, Spain.
- <sup>c</sup> Departamento de Química y Bioquímica, Facultad de Farmacia, Universidad CEU San Pablo, 28668 Boadilla del Monte, Madrid, Spain.
- E-mail: flaga@ceu.es
- † Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/b000000x/
- ‡ Footnotes should appear here. These might include comments relevant to but not central to the matter under discussion, limited experimental and spectral data, and crystallographic data.
- J. Lee, A. Urban, X. Li, D. Su, G. Hautier and G. Ceder, *Science*, 2014, **343**, 519-522.
  - B. C. Melot and J. M. Tarascon, *Accounts of Chemical Research*, 2013, **46**, 1226-1238.
  - S. Laha, E. Moran, R. Saez-Puche, M. A. Alario-Franco, A. J. Dos santos-García, E. Gonzalo, A. Kuhn, S. Natarajan, J. Gopalakrishnan and F. Garcia-Alvarado, *Journal of Materials Chemistry A*, 2013, **1**, 10686-10692.
  - S. Laha, E. Morán, R. Sáez-Puche, M. Á. Alario-Franco, A. J. Dos santos-García, E. Gonzalo, A. Kuhn, F. García-Alvarado, T. Sivakumar, S. Tamilarasan, S. Natarajan and J. Gopalakrishnan, *Journal of Solid State Chemistry*, 2013, **203**, 160-165.
  - Q. Q. Qiao, H. Z. Zhang, G. R. Li, S. H. Ye, C. W. Wang and X. P. Gao, *Journal of Materials Chemistry A*, 2013, **1**, 5262-5268.
  - A. Alexander, P. D. Battle, J. C. Burley, D. J. Gallon and C. P. Grey, *Journal of Materials Chemistry*, 2003, **13**, 2612-2616.
  - A. C. Larson and R. B. Von Dreele, *Los Alamos National Laboratory Report LAUR*, 2000, **86**.
  - W. Kraus and G. Nolze, *Journal of Applied Crystallography*, 1996, **29**, 301-303.
  - P. Strobel and B. Lambertandron, *Journal of Solid State Chemistry*, 1988, **75**, 90-98.

- 
10. H. J. Orman and P. J. Wiseman, *Acta Crystallographica Section C-Crystal Structure Communications*, 1984, **40**, 12-14.
  11. R. D. Shannon, *Acta Crystallographica Section A*, 1976, **32**, 751-767.
  12. R. I. Dass, J. Q. Yan and J. B. Goodenough, *Physical Review B*, 2004, **69**,
  13. U. Manju, V. P. S. Awana, H. Kishan and D. D. Sarma, *Physical Review B*, 2006, **74**.
  14. K. M. Shaju, K. V. Ramanujachary, S. E. Lofland, G. V. S. Rao and B. V. R. Chowdari, *Journal of Materials Chemistry*, 2003, **13**, 2633-2640.
  15. T. Yamashita and P. Hayes, *Applied Surface Science*, 2008, **254**, 2441-2449.
  16. J. C. Dupin, D. Gonbeau, P. Vinatier and A. Levasseur, *Physical Chemistry Chemical Physics*, 2000, **2**, 1319-1324.
  17. R. Dedryvere, D. Foix, S. Franger, S. Patoux, L. Daniel and D. Gonbeau, *Journal of Physical Chemistry C*, 2010, **114**, 10999-11008.
  18. T. Ohzuku and Y. Makimura, *Chemistry Letters*, 2001, 642-643.
  19. M. Sathiya, K. Ramesha, G. Rouse, D. Foix, D. Gonbeau, A. S. Prakash, M. L. Doublet, K. Hemalatha and J. M. Tarascon, *Chemistry of Materials*, 2013, **25**, 1121-1131.
  20. M. Sathiya, G. Rouse, K. Ramesha, C. P. Laisa, H. Vezin, M. T. Sougrati, M. L. Doublet, D. Foix, D. Gonbeau, W. Walker, A. S. Prakash, M. Ben Hassine, L. Dupont and J. M. Tarascon, *Nature Materials*, 2013, **12**, 827-835.
  21. T. A. Arinkumar, Y. Wu and A. Manthiram, *Chemistry of Materials*, 2007, **19**, 3067-3073.
  22. Y. Wu and A. Manthiram, *Electrochemical and Solid State Letters*, 2006, **9**, A221-A224.
  23. A. R. Armstrong, M. Holzapfel, P. Novak, C. S. Johnson, S.-H. Kang, M. M. Thackeray and P. G. Bruce, *Journal of the American Chemical Society*, 2006, **128**, 8694-8698.
  24. K. Numata, C. Sakaki and S. Yamanaka, *Solid State Ionics*, 1999, **117**, 257-263.
  25. K. Numata and S. Yamanaka, *Solid State Ionics*, 1999, **118**, 117-120.
  26. Z. H. Lu, L. Y. Beaulieu, R. A. Donabarger, C. L. Thomas and J. R. Dahn, *Journal of the Electrochemical Society*, 2002, **149**, A778-A791.
  27. Z. H. Lu and J. R. Dahn, *Journal of the Electrochemical Society*, 2002, **149**, A1454-A1459.
  28. Z. H. Lu and J. R. Dahn, *Journal of the Electrochemical Society*, 2002, **149**, A815-A822.
  29. T. Ohzuku, M. Kitagawa and T. Hirai, *Journal of the Electrochemical Society*, 1990, **137**, 769-775.
  30. J. M. Tarascon and D. Guyomard, *Journal of the Electrochemical Society*, 1991, **138**, 2864-2868.
  31. M. M. Thackeray, P. J. Johnson, L. A. Depicciotto, P. G. Bruce and J. B. Goodenough, *Materials Research Bulletin*, 1984, **19**, 179-187.
  32. J. M. Tarascon, G. Vaughan, Y. Chabre, L. Seguin, M. Anne, P. Strobel and G. Amatucci, *Journal of Solid State Chemistry*, 1999, **147**, 410-420.
  33. L. Daheron, R. Dedryvere, H. Martinez, M. Menetrier, C. Denage, C. Delmas and D. Gonbeau, *Chemistry of Materials*, 2008, **20**, 583-590.
  34. C. M. Julien and A. Mauger, *Ionics*, 2013, **19**, 951-988.

55